

WELCOME

The publishers of this Aviation Maintenance Technician Certification Series welcome you to the world of aviation maintenance. As you move towards EASA certification, you are required to gain suitable knowledge and experience in your chosen area. Qualification on basic subjects for each aircraft maintenance license category or subcategory is accomplished in accordance with the following matrix. Where applicable, subjects are indicated by an "X" in the column below the license heading.

For other educational tools created to prepare candidates for licensure, contact Aircraft Technical Book Company.

We wish you good luck and success in your studies and in your aviation career!

REVISION LOG

VERSION	EFFECTIVE DATE	DESCRIPTION OF CHANGE
001	2020 02	Module Creation and Release
001.1	2021 10	Corrected description of file types (Sub-Module 07, Pages 3.15-3.16)
001.2	2023 04	Submodule 8 - Added content on Friction and Mechanical lock blind rivet procedures. Inclusion of Measurement Standards for clarification, page iv. Minor appearance and format updates.

MODULE EDITIONS AND UPDATES

ATB EASA Modules are in a constant state of review for quality, regulatory updates, and new technologies. This book's edition is given in the revision log above. Update notices will be available Online at www.actechbooks.com/revisions.html

If you would like to be notified when changes occur, please join our mailing list at www.actechbooks.com

7.8 - RIVETS

RIVETED JOINTS, RIVET SPACING, AND PITCH

SOLID SHANK RIVET

The solid shank rivet is the most common type of rivet used in aircraft construction. Used to join aircraft structures, solid shank rivets are one of the oldest and most reliable types of fastener. Widely used in the aircraft manufacturing industry, solid shank rivets are relatively low-cost, permanently installed fasteners. They are faster to install than bolts and nuts since they adapt well to automatic, high-speed installation tools. Rivets should not be used in thick materials or in tensile applications, as their tensile strengths are quite low relative to their shear strength. The longer the total grip length, the more difficult it becomes to lock the rivet.

Riveted joints are neither airtight nor watertight unless special seals or coatings are used. Since rivets are permanently installed, they must be removed by drilling them out, a laborious task.

Before installation, the rivet consists of a smooth cylindrical shaft with a factory head on one end. The opposite end is called the bucktail. To secure two or more pieces of sheet metal together, the rivet is placed into a hole cut just a bit larger in diameter than the rivet itself. Once placed in this predrilled hole, the bucktail is upset or deformed by any of several methods from hand-held hammers to pneumatically driven squeezing tools. This action causes the rivet shank protruding through the sheet metal to form a shop head of approximately 1-1/2 times the diameter of the rivet and reduces the length to 1/2 times the diameter of the rivet.

Rivet Head Shape

Solid rivets are available in several head shapes, but the universal and the 100° countersunk head are the most commonly used in aircraft structures. Universal head rivets were developed specifically for the aircraft industry and designed as a replacement for both the round and brazier head rivets.

These rivets replaced all protruding head rivets and are used primarily where the protruding head has no aerodynamic significant. (*Figure 8-1*)

The countersunk head angle can vary from 60° to 120°, but the 100° has been adopted as standard because this head style provides the best possible compromise. The countersunk rivet is primarily intended for use when aerodynamics smoothness is critical, such as on the external surface of a high-speed aircraft.

Rivet Construction

Rivets are available in a wide variety of alloys, head shapes, and sizes and have a wide variety of uses in aircraft structure. Rivets that are satisfactory for one part of the aircraft are often unsatisfactory for another part. Therefore, it is important that an aircraft technician know the strength and properties of the various types of rivets and how to identify them.

Solid Rivet Types

Solid rivets are classified by their head shape, by the material from which they are manufactured, and by their size. Identification codes used are derived from a combination of the Military Standard (MS) and National Aerospace Standard (NAS) systems. For example, the prefix MS identifies hardware that conforms to military standards. Letters following the head-shaped code identify the material or alloy from which the rivet was made. The alloy code is followed by two numbers separated by a dash. The first number is the numerator of a fraction, which specifies the shank diameter in thirty-seconds of an inch. The second number is the numerator of a fraction in sixteenths of an inch and identifies the length of the rivet. Rivet head shapes and their identifying code numbers are shown in *Figure 8-2*.

The most frequently used repair rivet is the AD rivet because it can be installed in the received condition. Some rivet alloys, such as DD rivets (alloy 2024-T4), are too hard to drive in the received condition and must be annealed before they can be installed. Typically, these rivets are annealed and stored in a freezer to retard



Figure 8-1. Solid shank rivet styles.

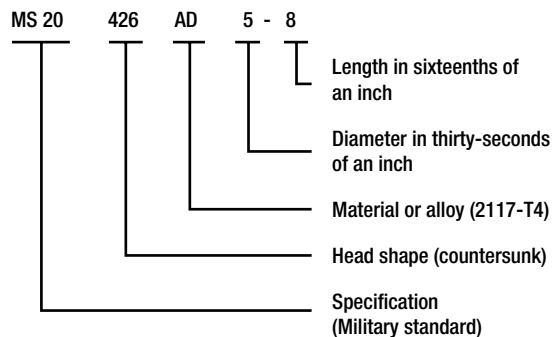


Figure 8-2. Rivet head shapes and their identifying code numbers.

hardening, which has led to the nickname "ice box rivets." They are removed from the freezer just prior to use. Most DD rivets have been replaced by E-type rivets which can be installed in the received condition.

The size, and strength required in a rivet are governed by such factors as the kind of forces present at the point riveted, the kind and thickness of the material to be riveted, and the location of the part on the aircraft. The type of head needed for a particular job is determined by where it is to be installed. Countersunk head rivets should be used where a smooth aerodynamic surface is required. Universal head rivets may be used in most other areas.

The size (or diameter) of the selected rivet shank should correspond in general to the thickness of the material being riveted. If an excessively large rivet is used in a thin material, the force necessary to drive the rivet properly causes an undesirable bulging around the rivet head. On the other hand, if an excessively small rivet diameter is selected for thick material, the shear strength of the rivet is not great enough to carry the load of the joint. As a general rule, the rivet diameter should be at least two and a half to three times the thickness of the thicker sheet. Rivets most commonly chosen in the assembly and repair of aircraft range from 3/32 inch to 3/8 inch in diameter. Ordinarily, rivets smaller than 3/32 inch in diameter are never used on any structural parts that carry stresses.

The proper sized rivets to use for any repair can also be determined by referring to the rivets (used by the manufacturer) in the next parallel row inboard on the wing or forward on the fuselage. Another method of determining the size of rivets to be used is to multiply the skin's thickness by 3 and use the next larger size rivet corresponding to that calculation.

For example, if the skin is 0.040 inch thick, multiply 0.040 inch by 3 to get 0.120 inch and use the next larger size of rivet, 1/8 inch (0.125 inch).

When rivets are to pass completely through tubular members, select a rivet diameter equivalent to at least 1/8 the outside diameter of the tube. If one tube sleeves or fits over another, take the outside diameter of the outside tube and use one eighth of that distance as the minimum rivet diameter.

Whenever possible, select rivets of the same alloy number as the material being riveted. For example, use 1100 and 3003 rivets on parts fabricated from 1100 and 3003 alloys, and 2117-1 and 2017-T rivets on parts fabricated from 2017 and 2024 alloys.

The size of the formed head is the visual standard of a proper rivet installation. The minimum and maximum sizes, as well as the ideal size, are shown in *Figure 8-3*.

Rivet Strength

For structural applications, the strength of the replacement rivets is of primary importance. (*Figure 8-4*) Rivets made of material that is lower in strength should not be used.

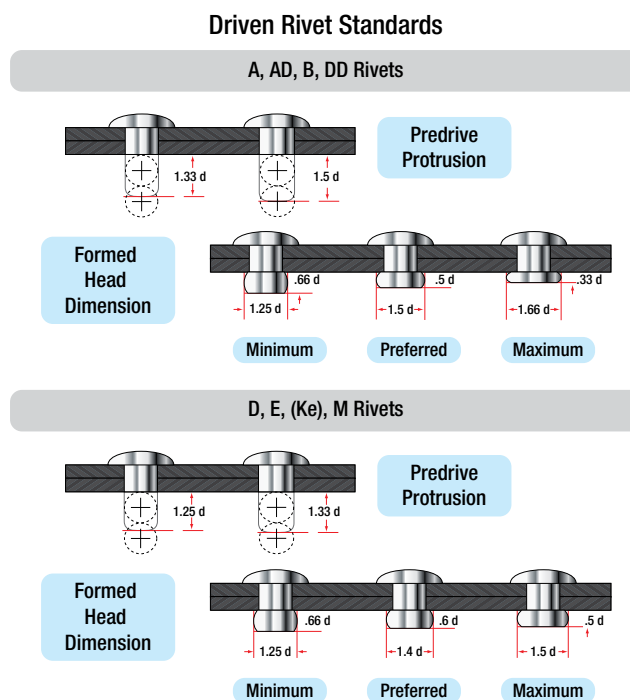


Figure 8-3. Rivet formed head dimensions.

The 2117-T rivet is used for general repair work, since it requires no heat treatment, is fairly soft and strong, and is highly corrosion resistant when used with most types of alloys. Always consult the maintenance manual for correct rivet type and material. The type of rivet head to select for a particular repair job can be determined by referring to the type used within the surrounding area by the manufacturer. A general rule to follow on a flush-riveted aircraft is to apply flush rivets on the upper surface of the wing and stabilizers, on the lower leading edge back to the spar, and on the fuselage back to the high point of the wing. Use universal head rivets in all other surface areas. Whenever possible, select rivets of the same alloy number as the material being riveted.

Stresses Applied to Rivets

Shear is one of the two stresses applied to rivets. The shear strength is the amount of force required to cut a rivet that holds two or more sheets of material together. If the rivet holds two parts, it is under single shear; if it holds three sheets or parts, it is under double shear. To determine the shear strength, the diameter of the rivet to be used must be found by multiplying the thickness of the skin material by 3.

For example, a material thickness of 0.040 inch multiplied by 3 equals 0.120 inch. In this case, the rivet diameter selected would be 1/8 (0.125) inch.

Tension is the other stress applied to rivets. The resistance to tension is called bearing strength and is the amount of tension required to pull a rivet through the edge of two sheets riveted together or to elongate the hole.

Rivet Length

To determine the total length of a rivet to be installed, the combined thickness of the materials to be joined must first be known. This measurement is known as the grip length. The total length of the rivet equals the grip length plus the amount of rivet shank needed to form a proper shop head. The latter equals one and a half times the diameter of the rivet shank. Where A is total rivet length, B is grip length, and C is the length of the material needed to form a shop head, this formula can be represented as $A = B + C$. (Figure 8-3)

REPAIR LAYOUT

Repair layout involves determining the number of rivets required, the proper size and style of rivets to be used, their material, temper condition and strength, the size of the holes, the distances between the holes, and the distance between the holes and the edges of the patch. Distances are measured in terms of rivet diameter.

RIVET SPACING

Rivet spacing is measured between the centerlines of rivets in the same row. The minimum spacing between protruding head rivets shall not be less than 3-1/2 times the rivet diameter. The minimum spacing between flush head rivets shall not be less than 4 times the diameter of the rivet. These dimensions may be used as the minimum spacing except when specified differently in a specific repair procedure or when replacing existing rivets.







Standard Rivet Alloy Code Markings	
<p>Alloy code—A Alloy—1100 or 3003 aluminum Head marking—None</p>  <p>Shear strength—10 kilopounds per square inch (KSI) Nonstructural uses only</p>	<p>Alloy code—B Alloy—5056 aluminum Head marking—raised cross</p>  <p>Shear strength—28 KSI</p>
<p>Alloy code—AD Alloy—2117 aluminum Head marking—Dimple</p>  <p>Shear strength—30 KSI</p>	<p>Alloy code—D Alloy—2017 aluminum Head marking—Raised dot</p>  <p>Shear strength—38 KSI 38 KSI When driven as received 34 KSI When re-heat treated</p>
<p>Alloy code—DD Alloy—2024 aluminum Head marking—Two bars (raised)</p>  <p>Shear strength—41 KSI Must be driven in "W" condition (Ice-Box)</p>	<p>Alloy code—E, [KE*] *Boeing code Alloy—7050 aluminum Head marking—Raised ring</p>  <p>Shear strength—43 KSI Replacement for DD rivet to be driven in "T" condition</p>

Figure 8-4. Rivet alloy strength.

On most repairs, the general practice is to use the same rivet spacing and edge distance (distance from the center of the hole to the edge of the material) that the manufacturer used.


Edge Distance

Edge distance, also called edge margin by some manufacturers, is the distance from the center of the first rivet to the edge of the sheet. It should not be less than 2 or more than 4 rivet diameters and the recommended edge distance is about 2-1/2 rivet diameters. The minimum edge distance for universal rivets is 2 times the diameter of the rivet; the minimum edge distance for countersunk rivets is 2-1/2 times the diameter of the rivet. If rivets are placed too close to the edge of the sheet, the sheet may crack or pull away from the rivets. If they are spaced too far from the edge, the sheet is likely to turn up at the edges. (Figure 8-5)

It is good practice to lay out the rivets a little further from the edge so that the rivet holes can be oversized without violating the edge distance minimums. Add 1/16 inch to the minimum edge distance or determine the edge distance using the next size of rivet diameter.

Rivet Pitch

Rivet pitch is the distance between the centers of neighboring rivets in the same row. The smallest allowable rivet pitch is 3 rivet diameters. The average rivet pitch usually ranges from 4 to 6 rivet diameters,

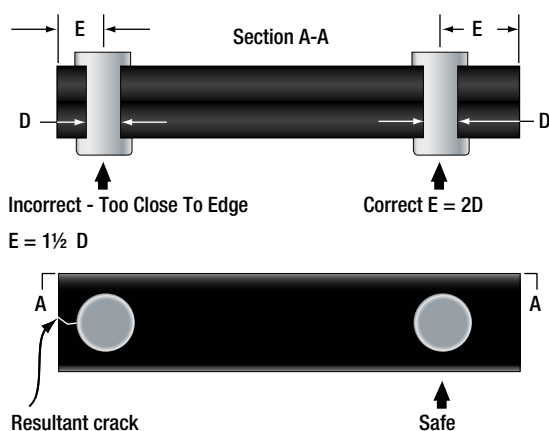

Edge Distance/Edge Margin	Minimum Edge Distance	Preferred Edge Distance
Protruding Head Rivets	2 D	2 D + 1/16"
Countersunk Rivets	2½ D	2½ D + 1/16"

Figure 8-5. Minimum edge distance.

although in some instances rivet pitch could be as large as 10 rivet diameters. Rivet spacing on parts that are subjected to bending moments is often closer to the minimum spacing to prevent buckling of the skin between the rivets. The minimum pitch also depends on the number of rows of rivets.

One-and three-row layouts have a minimum pitch of 3 rivet diameters, a two-row layout has a minimum pitch of 4 rivet diameters. The pitch for countersunk rivets is larger than for universal head rivets. If the rivet spacing is made at least 1/16 inch larger than the minimum, the rivet hole can be oversized without violating the minimum rivet spacing requirement. (Figure 8-6)

Transverse Pitch

Transverse pitch is the perpendicular distance between rivet rows. It is usually 75 percent of the rivet pitch.

RIVET LAYOUT EXAMPLE

The general rules for rivet spacing, as it is applied to a straight-row layout, are quite simple. In a one-row layout, find the edge distance at each end of the row and then lay off the rivet pitch (distance between rivets), as

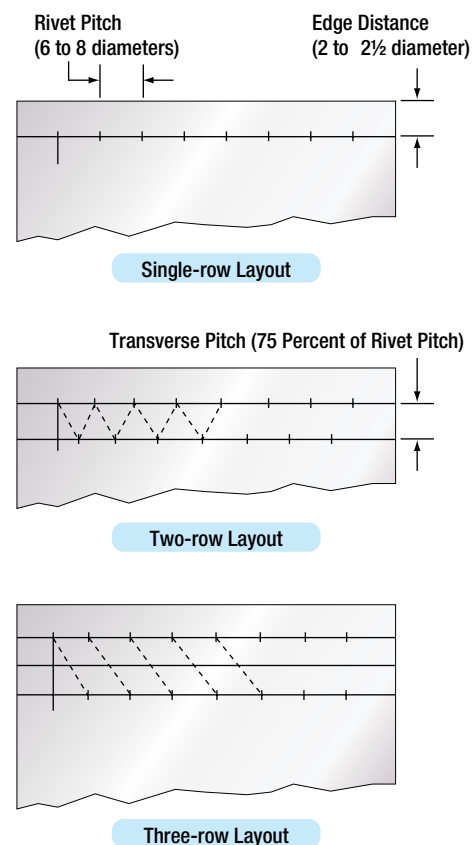


Figure 8-6. Rivet spacing.

Rivet Spacing	Minimum Spacing	Preferred Spacing
1 and 3 rows protruding head rivet layout	3D	3D + 1/16"
2 row protruding head rivet layout	4D	4D + 1/16"
1 and 3 rows countersunk head rivet layout	3/1/2D	3/1/2D + 1/16"
2 row countersunk head rivet layout	4/1/2D	4/1/2D + 1/16"

Figure 8-7. Rivet layout.

shown in *Figure 8-7*. In a two-row layout, lay off the first row, place the second row a distance equal to the transverse pitch from the first row, and then lay off rivet spots in the second row so that they fall midway between those in the first row. In the three-row layout, first lay off the first and third rows, then use a straightedge to determine the second row rivet spots.

When splicing a damaged tube, and the rivets pass completely through the tube, space the rivets four to seven rivet diameters apart if adjacent rivets are at right angles to each other, and space them five to seven rivet diameters apart if the rivets are parallel to each other. The first rivet on each side of the joint should be no less than 2-1/2 rivet diameters from the end of the sleeve.

TOOLS USED FOR RIVETING AND DIMPLING

The various tools needed in the normal course of driving rivets include drills, reamers, rivet cutters or nippers, bucking bars, riveting hammers, draw sets, dimpling dies or other types of countersinking equipment, rivet guns, and squeeze riveters.

HAND TOOLS

A variety of hand tools are used in the normal course of driving and setting rivets. They include rivet cutters, bucking bars, hand riveters, countersinks, and dimpling tools.

Rivet Cutter

The rivet cutter is used to trim rivets when rivets of the required length are unavailable. (*Figure 8-8*) To use the rotary rivet cutter, insert the rivet in the correct hole, place the required number of shims under the rivet head, and squeeze the cutter as if it were a pair of pliers. Rotation of the disks cuts the rivet to give the right length, which is determined by the number of shims inserted under the head. When using a large rivet cutter, place it in a vise, insert the rivet in the proper hole, and cut by pulling the handle, which shears off the rivet.

Bucking Bar

The bucking bar, sometimes called a dolly, bucking iron, or bucking block, is a heavy chunk of steel whose counter vibration during installation contributes to proper rivet installation. They come in a variety of shapes and sizes, and their weights range from 0.5 to 4.5 kg, depending upon the nature of the work.

Bucking faces must be hard enough to resist indentation and remain smooth, but not hard enough to shatter. The bar usually has a concave face to conform to the shape of the shop head to be made. When selecting a bucking bar, the first consideration is shape. (*Figure 8-9*)

If the bar does not have the correct shape, it deforms the rivet head; if the bar is too light, it does not give the necessary bucking weight, and the material may become bulged toward the shop head. If the bar is too heavy, its weight and the bucking force may cause the material to bulge away from the shop head.



Figure 8-8. Rivet cutters.



Figure 8-9. Bucking bars.

This tool is used by holding it against the shank end of a rivet while the shop head is being formed. Always hold the face of the bucking bar at right angles to the rivet shank. Failure to do so causes the rivet shank to bend with the first blows of the rivet gun and causes the material to become marred with the final blows. The bucking bar must hold the bucking bar in place until the rivet is completely driven. If the bucking bar is removed while the gun is in operation, the rivet set may be driven through the material. Allow the weight of the bucking bar to do most of the work and do not bear down too heavily on the shank of the rivet. The operator's hands merely guide the bar and supply the necessary tension and rebound action.

Coordinated bucking allows the bucking bar to vibrate in unison with the gun set. With experience, a high degree of skill can be developed.

Defective rivet heads can be caused by lack of proper vibrating action, the use of a bucking bar that is too light or too heavy, and failure to hold the bucking bar at right angles to the rivet. The bars must be kept clean, smooth, and well polished. Their edges should be slightly rounded to prevent marring the material surrounding the riveting operation.

Rivet Hand Set

A hand rivet set is a tool equipped with a die for driving a particular type rivet. Rivet sets are available to fit every size and shape of rivet head. The ordinary set is made of 1/2 inch carbon tool steel about 15 cm in length and is knurled to prevent slipping in the hand. Only the face of the set is hardened and polished.

Sets for universal rivets are recessed (or cupped) to fit the rivet head. In selecting the correct set, be sure it provides the proper clearance between the set and the sides of the rivet head and between the surfaces of the metal and the set. Flush or flat sets are used for countersunk and flathead rivets. To seat flush rivets properly, be sure that the flush sets are at least 1 inch in diameter.

Dimpling Dies

Dimpling is done with a male and female die (punch and die set). The male die has a guide the size of the rivet hole and with the same degree of countersink as the rivet. The female die has a hole with a corresponding degree of countersink into which the male guide fits.

Chip Chasers

The chip chaser is designed to remove chips and burrs lodged between sheets of metal after drilling holes for riveting. Chip chasers have a plastic molded handle and a flexible steel blade with a hook in the end. (*Figure 8-10*)

POWERED TOOLS

The most common power tools used in riveting are the pneumatic rivet gun, rivet squeezers, and the microshaver.

Pneumatic Rivet Gun

The pneumatic rivet gun is the most common rivet setting tool used in airframe repair work. It is available in many sizes and types. (*Figure 8-11*) The manufacturer's recommended capacity for each gun is usually stamped on the barrel. Pneumatic guns operate on air pressure of 6.5 to 7 kg per square cm and are used in conjunction with interchangeable rivet sets. Each set is designed to fit the specific type of rivet and the location of the work. The shank of the set is designed to fit into the rivet gun. An air-driven hammer inside the barrel of the gun supplies force to buck the rivet. Slow hitting rivet guns that strike from 900 to 2 500 blows per minute are the most common type. (*Figure 8-12*)



Figure 8-10. Chip chaser.



Figure 8-11. Pneumatic rivet gun.

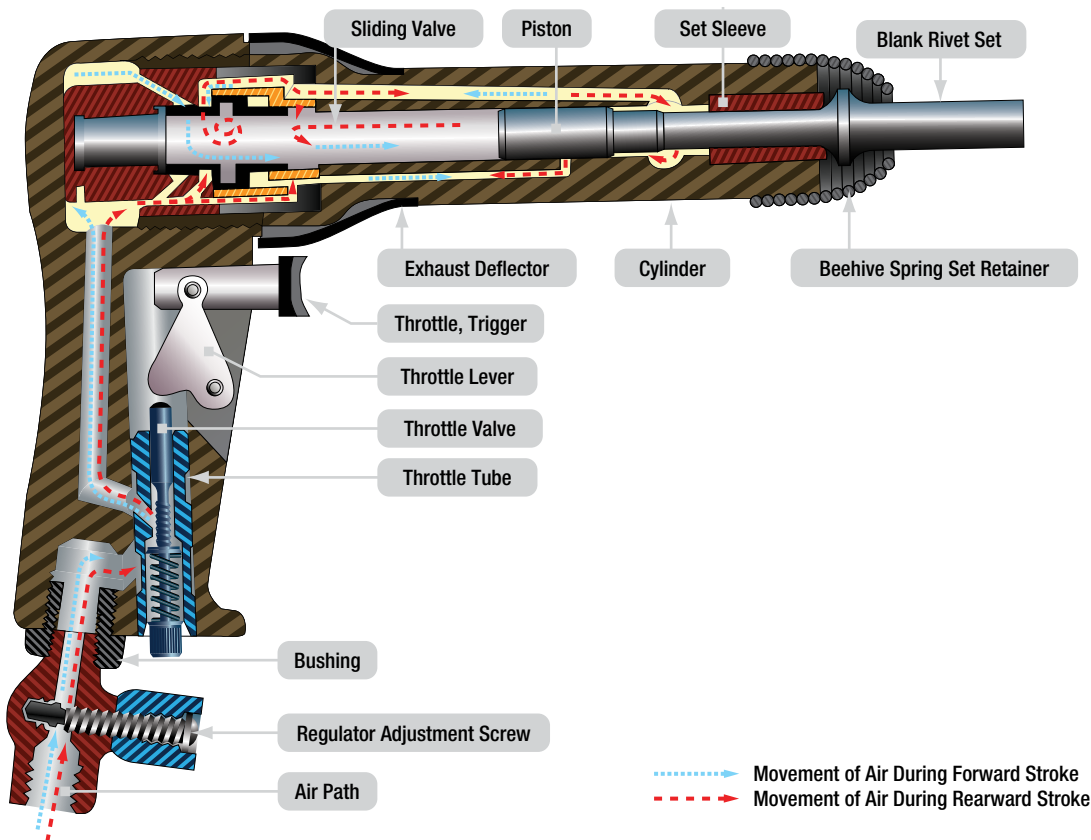


Figure 8-12. Components of a rivet gun.

These blows are slow enough to be easily controlled and heavy enough to do the job. These guns are sized by the largest rivet size continuously driven with size often based on the "X" series. A 4X gun (dash 8 or 1/4 rivet) is used for normal work. The less powerful 3X gun is used for smaller rivets in thinner structure. 7X guns are used for large rivets in thicker structures. A rivet gun should upset a rivet in 1 to 3 seconds. With practice, an aircraft technician learns the length of time needed to hold down the trigger.

A rivet gun with the correct header must be held snugly against the rivet head and perpendicular to the surface while a bucking bar of the proper weight is held against the opposite end. The force of the gun must be absorbed by the bucking bar and not the structure being riveted. When the gun is triggered, the rivet is driven.

Always make sure the correct rivet header and the retaining spring are installed. Test the rivet gun on a piece of wood and adjust the air valve to a setting that is comfortable for the operator. The driving force of the rivet gun is adjusted by a needle valve on the handle. Adjustments should never be tested against anything

harder than a wooden block to avoid header damage. If the adjustment fails to provide the best driving force, a different size gun is needed. A gun that is too powerful is hard to control and may damage the work. On the other hand, if the gun is too light, it may work harden the rivet before the head can be fully formed.

The riveting action should start slowly and be one continuous burst. If the riveting starts too fast, the rivet header might slip off the rivet and damage the rivet (smiley) or damage the skin (eyebrow). Try to drive the rivets within 3 seconds, because the rivet will work harden if the driving process takes too long. The dynamic of the driving process has the gun hitting, or vibrating, the rivet and material, which causes the bar to bounce, or counter vibrate. These opposing blows (low frequency vibrations) squeeze the rivet, causing it to swell and then form the upset head. Some precautions to be observed when using a rivet gun are:

1. Never point a rivet gun at anyone at any time. A rivet gun should be used for one purpose only, to drive or install rivets.
2. Never depress the trigger mechanism unless the set is held tightly against a block of wood or rivet.

- Always disconnect the air hose from the rivet gun when it is not in use for any appreciable length of time.

Rivet Sets/Headers

Pneumatic guns are used in conjunction with interchangeable rivet sets or headers. Each is designed to fit the type of rivet and location of the work. The shank of the rivet header is designed to fit into the rivet gun. An appropriate header must be a correct match for the rivet being driven.

Flush headers come in various sizes. Smaller ones concentrate the driving force in a small area for maximum efficiency. Larger ones spread the driving force over a larger area and are used for the riveting of thin skins.

Non-flush headers should fit to contact about the center two thirds of the rivet head. Care must be taken to match the size of the rivet. A header that is too small marks the rivet; while one too large marks the material.

Rivet headers are made in a variety of styles. The short, straight header is best so the gun can be brought close to the work. Offset headers may be used to reach rivets in obstructed places. Long headers can be necessary when the gun cannot be brought close to the work due to structural interference. Rivet headers should be kept clean. (Figure 8-13)

Compression Riveting

Compression riveting (squeezing) is of limited value because this method of riveting can be used only over the edges of sheets or assemblies where conditions permit, and where the reach of the rivet squeezer is deep enough. The three types of rivet squeezers - hand, pneumatic, and pneudraulic - operate on the same principles. In



Figure 8-13. Rivet headers.

the hand rivet squeezer, compression is supplied by hand pressure; in the pneumatic rivet squeezer, by air pressure; and in the pneudraulic, by a combination of air and hydraulic pressure. One jaw is stationary and serves as a bucking bar, the other jaw is movable and does the upsetting. Riveting with a squeezer is a quick method and requires only one operator. (Figure 8-14)

The manufactured head end set is placed on the stationary jaw whenever possible. During some operations, it may be necessary to reverse the end sets, placing the manufactured head end set on the movable jaw.

REUSABLE SHEET METAL FASTENERS

Reusable sheet metal fasteners temporarily hold drilled sheet metal parts accurately in position for riveting or drilling. If sheet metal parts are not held tightly together, they separate while being riveted or drilled. The Cleco fastener is the most commonly used sheet metal holder. (Figure 8-15)

Cleco Fasteners

The Cleco fastener consists of a steel cylinder body with a plunger on the top, a spring, a pair of stepcut locks, and a spreader bar. These fasteners come in various sizes and are color coded for easy recognition.

3/32	(#40)	Zink
1/8	(#30)	Copper
5/32	(#21)	Black
3/16	(#10)	Brass
1/4	(1/4")	Copper



Figure 8-14. Hand and pneumatic type rivet squeezers.

A special type of pliers fits the six different sizes. When installed correctly, the reusable Cleco fastener keeps the holes in the separate sheets aligned. (Figure 8-16)

Hex Nut and Wing Nut Temporary Fasteners

Hex nut and wing nut fasteners are used to temporarily fasten sheets of metal when higher clamp up pressure is required. (Figure 8-17) Hex nut fasteners provide up to 135 kilograms of clamping force with the advantage of quick installation and removal.

RIVETING PROCEDURES

UNIVERSAL HEAD RIVETS

The riveting procedure consists of preparing the hole, drilling, and driving the rivets.



Figure 8-15. A part temporarily held together with Cleco fasteners.



Figure 8-16. Celco pliers ready to insert a 3/32" Cleco fastener.



Figure 8-17. A wing nut temporary fastener.

Hole Preparation

It is very important that the rivet hole be of the correct size and shape and free from burrs. If the hole is too small, the protective coating is scratched from the rivet when the rivet is driven through the hole. If the hole is too large, the rivet does not fill the hole completely. When it is bucked, the joint does not develop its full strength, and structural failure may occur at that spot.

If countersinking is required, consider the thickness of the metal and adopt the countersinking method recommended for that thickness. If dimpling is required, keep hammer blows or dimpling pressures to a minimum so that no undue work hardening occurs in the surrounding area.

Drilling

When drilling holes in new pieces of metal being used for a repair, they may be drilled with either a light power drill or a hand drill. The recommended clearance drill bits for the common rivet diameters are shown in Figure 8-18. Hole sizes for other fasteners are normally found on work documents, prints, or in manuals.

Before drilling, center punch all rivet locations. The center punch mark should be large enough to prevent the drill from slipping out of position, yet it must not dent the surface surrounding the center punch mark. Place a bucking bar behind the metal during punching to help prevent denting. To make a rivet hole the correct size, first drill a slightly undersized hole (pilot hole). Ream the pilot hole with a twist drill of the appropriate size to obtain the required dimension.

To drill, proceed as follows:

1. Ensure the bit is the correct size and shape.
2. Place the drill in the center-punched mark.
When using a power drill, rotate the bit a few turns before starting the motor.

Rivet Diameter (in)	Drill Size	
	Pilot	Final
3/32	3/32 (0.0937)	#40 (0.098)
1/8	1/8 (0.125)	#30 (0.1285)
5/32	5/32 (0.1562)	#21 (0.159)
3/16	3/16 (0.1875)	#11 (0.191)
1/4	1/4 (0.250)	F (0.257)

Figure 8-18. Drill sizes for standard rivets.

3. While drilling, always hold the drill at a 90° angle to the work or the curvature of the material.
4. Avoid excessive pressure, let the bit do the cutting, and never push the bit through stock.
5. Remove all burrs with a countersink or a file.
6. Clean away all drill chips.

When holes are drilled through sheet metal, small burrs are formed around the edge of the hole. This is especially true when using a hand drill because the drill speed is slow and there is a tendency to apply more pressure per drill revolution. Remove all burrs with a burr remover or larger size drill bit before riveting.

Driving The Rivet

Before driving any rivets into the sheet metal parts, be sure all holes line up perfectly, all shavings and burrs have been removed, and the parts to be riveted are securely fastened with temporary fasteners. Depending on the job, the riveting process may require one or two people. In solo riveting, the riveter holds a bucking bar with one hand and operates a riveting gun with the other.

If the job requires two aircraft technicians, a shooter, and a bucker work together as a team to install rivets. An important component of team riveting is an efficient signaling system that communicates the status of the riveting process. This signaling system usually consists of tapping the bucking bar against the work. One tap may mean not fully seated, hit it again, while two taps may mean good rivet, and three taps may mean bad rivet, remove and drive another.

Once the rivet is installed, there should be no evidence of rotation of rivets or looseness of riveted parts. After the trimming operation, examine for tightness. A tight stem is one indication of an acceptable rivet installation. Any degree of looseness indicates an oversize hole and requires replacement of the rivet with an oversize shank diameter rivet.

COUNTERSUNK RIVETS

An improperly made countersink reduces the strength of a flush-riveted joint and may even cause failure of the sheet or the rivet head. The two methods of countersinking commonly used for flush riveting in aircraft construction and repair are:

- Machine or drill countersinking.
- Dimpling or press countersinking.

The proper method for any particular application depends on the thickness of the parts to be riveted, the height and angle of the countersunk head, the tools available, and accessibility. When using countersunk rivets, it is necessary to make a conical recess in the skin for the head. The type of countersink required depends upon the relation of the thickness of the sheets to the depth of the rivet head. Use the proper degree and diameter countersink and cut only deep enough for the rivet head and metal to form a flush surface.

Countersinking is an important factor in the design of fastener patterns, as the removal of material in the countersinking process necessitates an increase in the number of fasteners to assure the required load-transfer strength. If countersinking is done on metal below a certain thickness, a knife edge with less than the minimum bearing surface or actual enlarging of the hole may result.

In primary structure and pressurized skin repairs, some manufacturers are recommending the countersink depth be no more than 2/3 the outer sheet thickness or down to 0.020 inch minimum fastener shank depth, whichever is greater. Dimple the skin if it is too thin for machine countersinking. (*Figure 8-19*)

Countersink Tools

While there are many types of countersink tools, the most commonly used has an included angle of 100°.

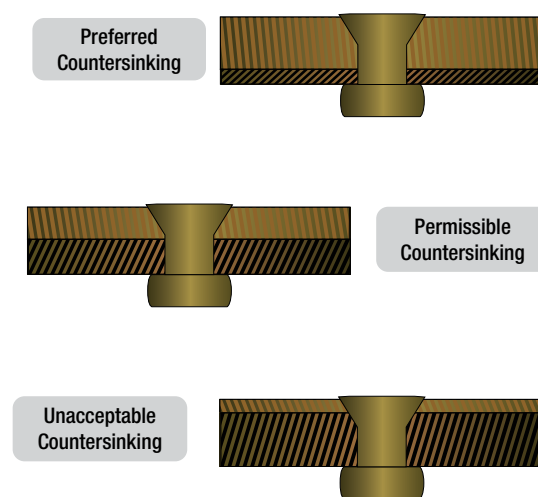


Figure 8-19. Countersinking dimensions.

Sometimes types of 82° or 120° are used to form countersunk wells. A six fluted countersink works best in aluminum. There are also four and three fluted countersinks, but those are harder to control from a chatter standpoint. A single flute type works best for corrosion resistant steel. (Figure 8-20)

The microstop countersink is the preferred tool for countersinking. (Figure 8-21)

It has an adjustable-sleeve cage that functions as a limit stop and holds the revolving countersink in a vertical position. It is recommended to test adjustments on a piece of scrap material before countersinking repair or replacement parts. Freehand countersinking is needed where a micro-stop countersink cannot fit. This method should be practiced on scrap material to develop the required skill. Holding the drill motor steady and perpendicular is as critical during this operation as when drilling.

Chattering is the most common problem encountered when countersinking. Some precautions that may eliminate or minimize chatter include:

- Use sharp tooling.
- Use a slow speed and steady firm pressure.
- Use a piloted countersink with a pilot approximately 0.002 inch smaller than the hole.
- Use back-up material to hold the pilot steady when countersinking thin sheet material.

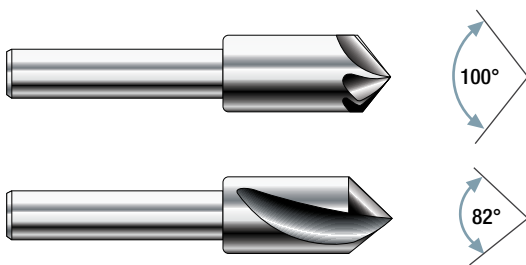


Figure 8-20. Countersinks.

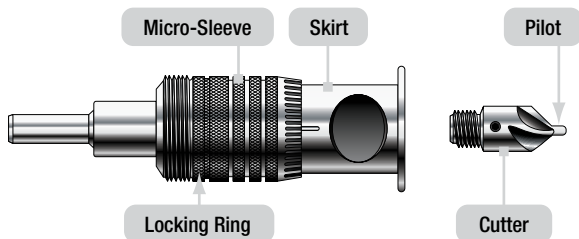


Figure 8-21. Microstop countersink.

- Use a cutter with a different number of flutes.
- Pilot drill an undersized hole, countersink, and then enlarge the hole to final size.

Dimpling

Dimpling is the process of making an indentation or a dimple around a rivet hole to make the top of the head of a countersunk rivet flush with the surface of the metal. Dimpling is done with a male and female die, or forms, often called punch and die set. The male die has a guide the size of the rivet hole and is beveled to correspond to the degree of countersink of the rivet head. The female die has a hole into which the male guide fits and is beveled to a corresponding degree of countersink.

When dimpling, rest the female die on a solid surface. Then, place the material to be dimpled on the female die. Insert the male die in the hole to be dimpled and, with a hammer, strike the male die until the dimple is formed. Two or three solid hammer blows should be sufficient. A separate set of dies is necessary for each size of rivet and shape of rivet head. (Figure 8-22)

Dimpling dies for light work can be used in portable pneumatic or hand squeezers. If the dies are used with a squeezer, they must be adjusted accurately to the thickness of the sheet being dimpled. A table riveter is also used for dimpling thin skin material and installing rivets. (Figure 8-23)

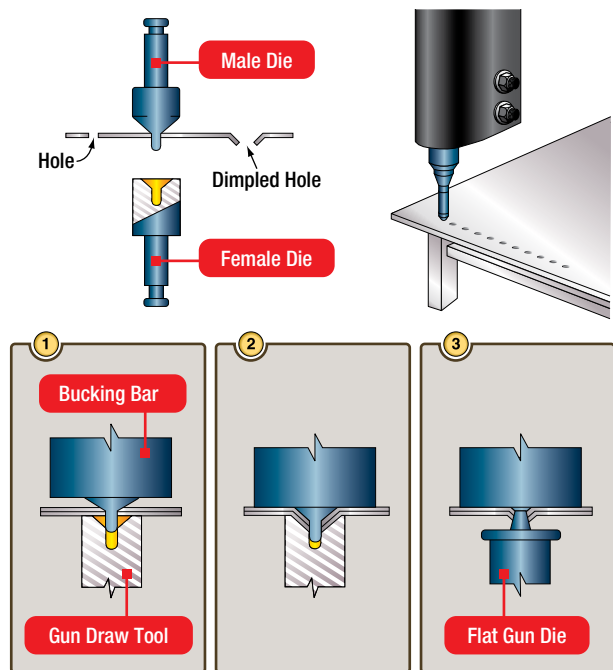


Figure 8-22. Dimpling techniques.

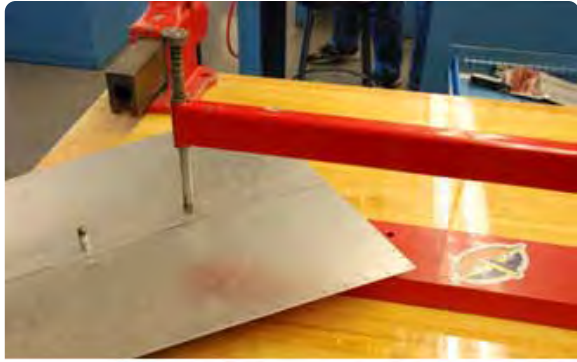


Figure 8-23. Examples of a table riveter and dimpler.

Radius Dimpling

Dimpling removes no metal and, due to the nestling effect, gives a stronger joint than the non-flush type. A dimpled joint reduces the shear loading on the rivet and places more load on the riveted sheets.

NOTE: Dimpling is also done for flush bolts and other flush fasteners.

Dimpling is required for sheets that are thinner than the minimum specified thickness for countersinking. However, dimpling is not limited to thin materials. Heavier parts may be dimpled without cracking by specialized hot dimpling equipment. The temper of the material, rivet size, and available equipment are all factors to be considered in dimpling.

Hot Dimpling

Hot dimpling is the process that uses heated dimpling dies to ensure the metal flows better during the dimpling process. Hot dimpling is often performed with large stationary equipment available in a sheet metal shop. The metal being used is an important factor because each metal presents different dimpling problems. For example, 2024-T3 aluminum alloy can be satisfactorily dimpled either hot or cold, but may crack in the vicinity of the dimple after cold dimpling because of hard spots in the metal. Hot dimpling prevents such cracking.

7075-T6 aluminum alloys are always hot dimpled. Magnesium alloys also must be hot dimpled because, like 7075-T6, they have low formability qualities. Titanium is another metal that must be hot dimpled because it is tough and resists forming.

A countersink well made to receive a dimple is called a subcountersink. These are most often seen where a thin web is attached to heavy structure. It is also used on thin gap seals, wear strips, and repairs for worn countersinks. (Figure 8-24)

Dimpling Inspection

To determine the quality of a dimple, it is necessary to make a close visual inspection. Several features must be checked. The rivet head should fit flush and there should be a sharp break from the surface into the dimple. The sharpness of the break is affected by dimpling pressure and metal thickness. Selected dimples should be checked by inserting a fastener to make sure that the flushness requirements are met. Cracked dimples are caused by poor dies, rough holes, or improper heating. Two types of cracks may form during dimpling:

- Radial cracks—start at the edge and spread outward as the metal within the dimple stretches. They are most common in 2024-T3. A rough hole or a dimple that is too deep causes such cracks.
- Circumferential cracks—downward bending into the draw die causes tension stresses in the upper portion of the metal. Under some conditions, a crack may be created that runs around the edge of the dimple. Such cracks do not always show since they may be underneath the cladding. When found, they are cause for rejection. These cracks are most common in hot dimpled 7075 T6 aluminum alloy material. The usual cause is insufficient dimpling heat.

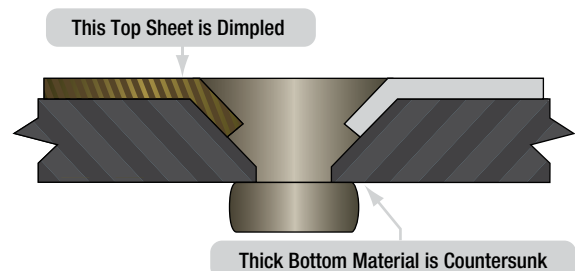


Figure 8-24. Pre-dimple and countersink method.

Microshavers

A microshaver is used if the smoothness of the material (such as skin) requires that all countersunk rivets be driven within a specific tolerance. (*Figure 8-25*)

This tool has a cutter, a stop, and two legs or stabilizers. The cutting portion of the microshaver is inside the stop. The depth of the cut can be adjusted by pulling outward on the stop and turning it in either direction (clockwise for deeper cuts).

The marks on the stop permit adjustments of 0.001 inch. If the microshaver is adjusted and held correctly, it can cut the head of a countersunk rivet to within 0.002 inch without damaging the surrounding material.

Adjustments should always be made first on scrap material. When correctly adjusted, the microshaver leaves a small round dot about the size of a pinhead on the microshaved rivet. It may occasionally be necessary to shave rivets, after driving to obtain the required flushness. Shear head rivets should never be shaved.

BLIND RIVETS

To install solid shank rivets, the aircraft technician must have access to both sides of a riveted structure or structural part. There are many places on an aircraft where this access is impossible or where limited space does not permit the use of a bucking bar. In these instances, it is not possible to use solid shank rivets, and special fasteners have been designed that can be bucked from the front.

Because these fasteners are often inserted in locations where one head, usually the shop head, cannot be seen, they are called blind rivets or blind fasteners.

Typically, the locking characteristics of a blind rivet are not as good as a driven rivet. Therefore, blind rivets are usually not used when driven rivets can be installed. Blind rivets shall not be used:

1. In fluid-tight areas.
2. On aircraft in air intake areas where rivet parts may be ingested by the engine.
3. On aircraft control surfaces, hinges, hinge brackets, flight control actuating systems, wing attachment fittings, landing gear fittings, on floats or amphibian hulls below the water level, or other heavily stressed locations on the aircraft.



Figure 8-25. Microshaver.

NOTE: For metal repairs to the airframe, the use of blind rivets must be specifically authorized by the airframe manufacturer.

The first blind fasteners were introduced in 1940 by the Cherry Rivet Company, and the aviation industry quickly adopted them. The past decades have seen a proliferation of blind fastening systems based on the original concept, which consists of a tubular rivet with a fixed head and a hollow sleeve. Inserted within the rivet's core is a stem that is enlarged or serrated on its exposed end when activated by a pulling-type rivet gun. The lower end of the stem extends beyond the inner sheet of metal. This portion contains a tapered joining portion and a blind head that has a larger diameter than the stem or the sleeve of the tubular rivet.

When the pulling force of the rivet gun forces the blind head upward into the sleeve, its stem upsets or expands the lower end of the sleeve into a tail. This presses the inner sheet upward and closes any space that might have existed between it and the outer sheet. Since the exposed head of the rivet is held tightly against the outer sheet by the rivet gun, the sheets of metal are clamped, or clinched, together.

Friction-Locked Blind Rivets

Standard self-plugging blind rivets consist of a hollow sleeve and a stem with increased diameter in the plug section. The blind head is formed as the stem is pulled into the sleeve. Friction-locked blind rivets have a multiple-piece construction and rely on friction to lock the stem to the sleeve. As the stem is drawn up into the rivet shank, the stem portion upsets the shank on the blind side, forming a plug in the hollow center of the rivet. The excess portion of the stem breaks off at a groove due to the continued pulling action of the rivet gun. (*Figure 8-26*)

Some types, such as the Cherry SPR® 3/32-inch Self-Plugging Rivet, are ideal for securing nutplates located in inaccessible and hard to reach areas where bucking or squeezing of solid rivets is unacceptable. (Figure 8-27) Friction-lock blind rivets are less expensive than mechanical-lock blind rivets and are sometimes used for nonstructural applications. Removal of friction-lock blind rivets consists of punching out the friction-lock stem and then treating it like any other rivet.

Mechanical-Lock Blind Rivets

The self-plugging, mechanical-lock blind rivet was developed to prevent the problem of losing the center stem due to vibration. This rivet has a device on the puller or rivet head that locks the center stem into place when installed. Bulbed, self-plugging, mechanically-locked blind rivets form a large, blind head that provides higher strength in thin sheets when installed. They may be used in applications where the blind head is formed against a dimpled sheet.

The CherryMAX® Bulbed blind rivet is one of the earlier types of mechanical-lock blind rivets developed. Their main advantage is the ability to replace a solid shank rivet size for size. The CherryMAX® Bulbed blind rivet consists of four parts:

1. A fully serrated stem with break notch, shear ring, and integral grip adjustment cone.
2. A driving anvil to ensure a visible mechanical lock with each fastener installation.
3. A separate, visible, and inspectable locking collar that mechanically locks the stem to the rivet sleeve.
4. A rivet sleeve with recess in the head to receive the locking collar.

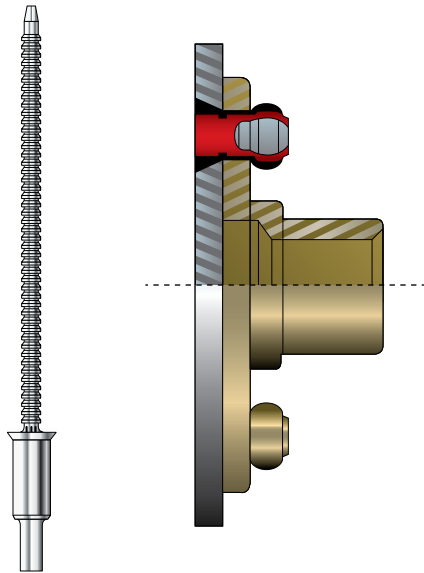


Figure 8-26. Friction-lock blind rivet.

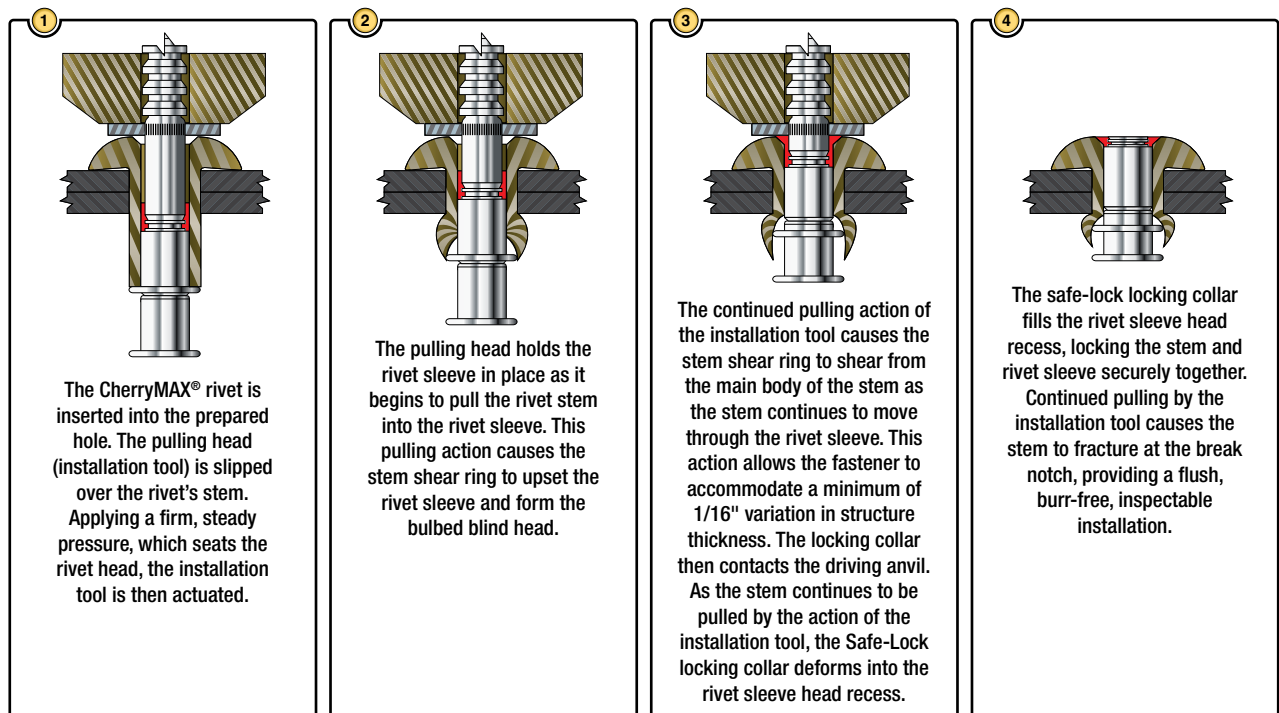


Figure 8-27. CherryMax® installation procedure.

It is called a bulbed fastener due to its large blind side bearing surface, developed during the installation process. These rivets are used in thin sheet applications and for use in materials that may be damaged by other types of blind rivets. This rivet features a safe-lock locking collar for more reliable joint integrity. The rough end of the retained stem in the center on the manufactured head must never be filed smooth because it weakens the strength of the locking, and the center stem could fall out.

The CherryMAX® mechanical-lock blind rivet is popular with general aviation repair shops because it features the one tool concept to install three standard rivet diameters and their oversize counterparts. (*Figure 8-28*) This rivet consists of a blind header, hollow rivet shell, locking (foil) collar, driving anvil, and pulling stem complete with wrapped locking collar. The rivet sleeve and the driving washer blind bulbed header takes up the extended shank and forms the bucktail.

Removal of Mechanically-Locked Blind Rivets

Mechanically-locked blind rivets are a challenge to remove because they are made from strong, hard metals. Lack of access poses yet another problem for the aviation technician. Designed for and used in difficult to reach locations means there is often no access to the blind side of the rivet or any way to provide support for the sheet metal surrounding the rivet's location when the aviation technician attempts removal.

The stem is mechanically locked by a small lock ring that needs to be removed first. Use a small center drill to provide a guide for a larger drill on top of the rivet stem and drill away the upper portion of the stem to destroy the lock. Try to remove the lock ring or use a prick punch or center punch to drive the stem down a little and remove the lock ring. After the lock ring is removed, the stem can be driven out with a drive punch. After the stem is removed, the rivet can be drilled out in the same way as a solid rivet. If possible, support the back side of the rivet with a backup block to prevent damage to the aircraft skin.

INSPECTION OF RIVETED JOINTS

To obtain high structural efficiency in the manufacture and repair of aircraft, an inspection must be made of all rivets before the part is put in service. This inspection consists of examining both the shop and manufactured

heads and the surrounding skin and structural parts for deformities. A scale or rivet gauge can be used to check the condition of the upset rivet head to see that it conforms to the proper requirements. Deformities in the manufactured head can be detected by the trained eye alone. (*Figure 8-29*)

Some common causes of unsatisfactory riveting are improper bucking, rivet set slipping off or being held at the wrong angle, and rivet holes or rivets of the wrong size. Additional causes for unsatisfactory riveting are countersunk rivets not flush with the well, work not properly fastened together during riveting, the presence of burrs, rivets too hard, too much or too little driving, and rivets out of line.

Occasionally, during an aircraft structural repair, it is wise to examine adjacent parts to determine the true condition of neighboring rivets. In doing so, it may be necessary to remove the paint. The presence of chipped or cracked paint around the heads may indicate shifted or loose rivets. Look for tipped or loose rivet heads. If the heads are tipped or if rivets are loose, they show up in groups of several consecutive rivets and probably tipped in the same direction. If heads that appear to be tipped are not in groups and are not tipped in the same direction, tipping may have occurred during some previous installation.

Inspect rivets known to have been critically loaded, but that show no visible distortion, by drilling off the head and carefully punching out the shank. If, upon examination, the shank appears joggled and the holes in the sheet misaligned, the rivet has failed in shear. Flush rivets that show head slippage within the countersink or dimple, indicating either sheet bearing failure or rivet shear failure, must be removed for inspection and replacement.

Joggles in removed rivet shanks indicate partial shear failure. Replace these rivets with the next larger size. Also, if the rivet holes show elongation, replace the rivets with the next larger size. Sheet failures such as tear-outs, cracks between rivets, and the like usually indicate damaged rivets. The complete repair of the joint may require replacement of the rivets with the next larger size.

REMOVAL OF RIVETS

When removing a rivet, work on the manufactured head. It is more symmetrical about the shank than the shop head, and there is less chance of damaging the rivet

hole or the material around it. To remove rivets, use hand tools, a power drill, or a combination of both. The procedure for universal or protruding head rivet removal is as follows:

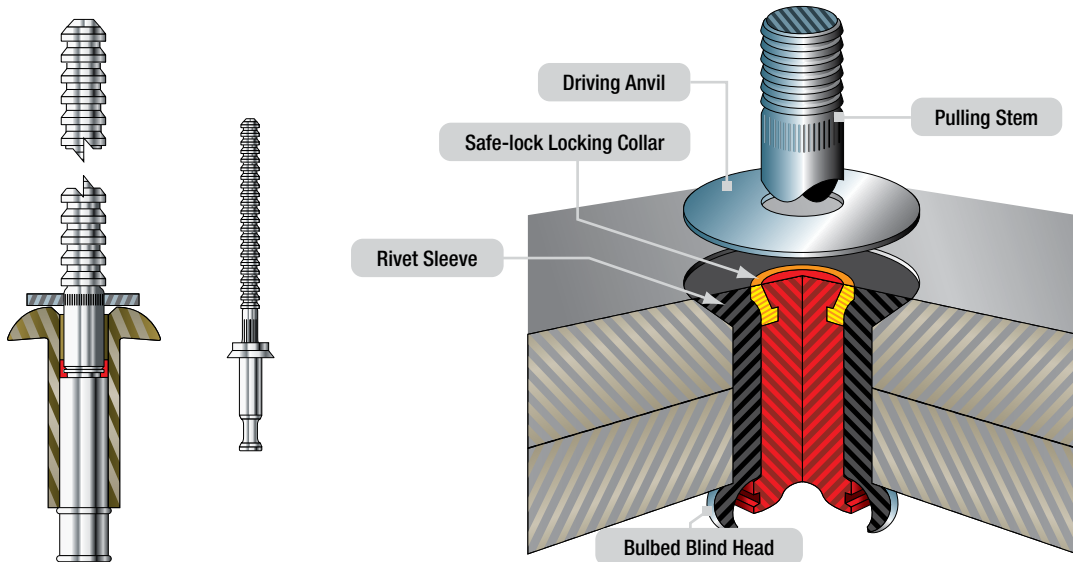


Figure 8-28. CherryMAX® rivet.

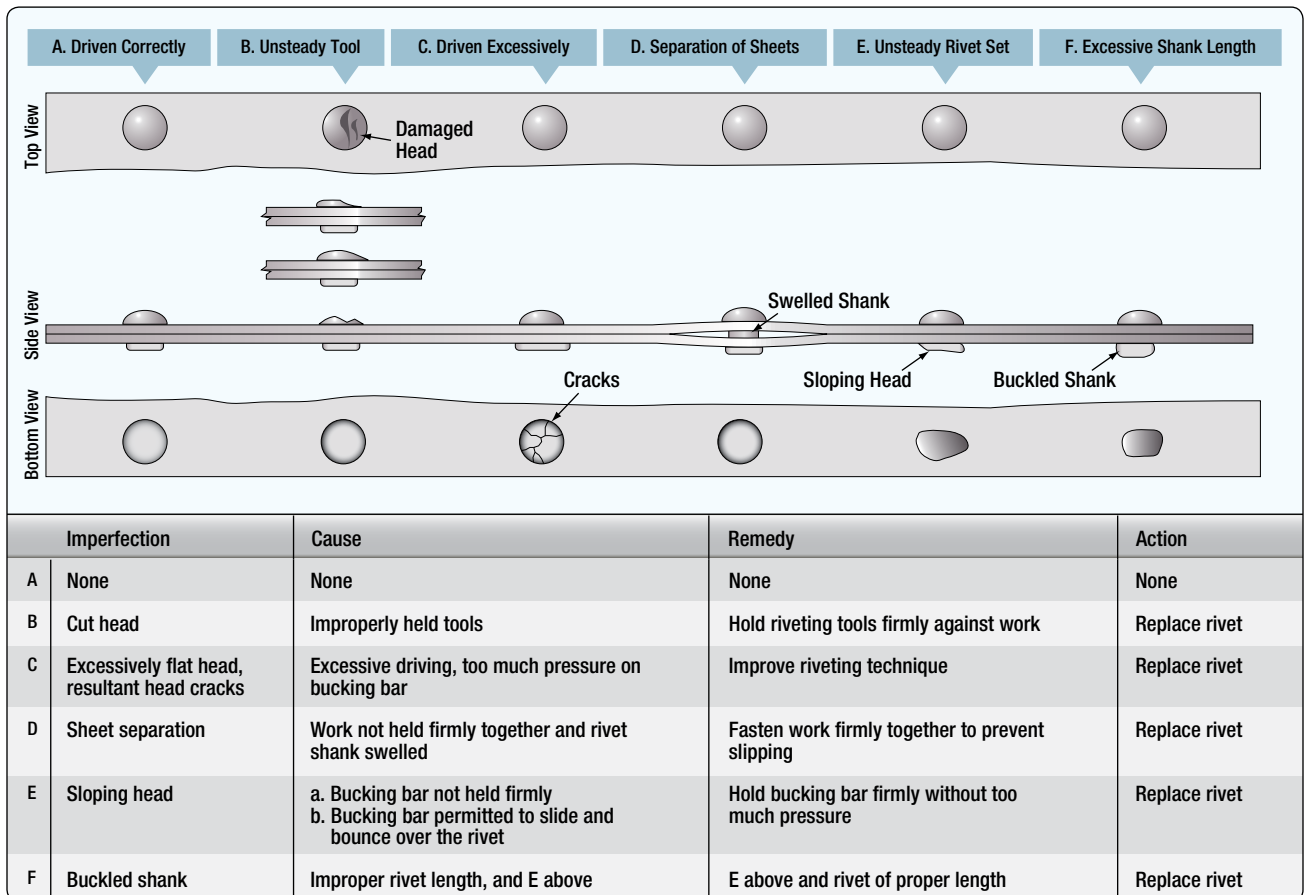


Figure 8-29. Rivet defects.

1. File a flat area on the head of the rivet and center punch the flat surface for drilling.
NOTE: On thin metal, back up the rivet on the upset head when center punching to avoid depressing the metal.
2. Use a drill bit one size smaller than the rivet shank to drill out the rivet head.
NOTE: When using a power drill, set the drill on the rivet and rotate the chuck several revolutions by hand before turning on the power. This procedure helps the drill cut a good starting spot and eliminates the chance of the drill slipping off and tracking across the metal.
3. Drill the rivet to the depth of its head, while holding the drill at a 90° angle. Do not drill too deeply, as the rivet shank will then turn with the drill and tear the surrounding metal.

NOTE: Rivet heads often break away and climb the drill, which is a signal to withdraw the drill.

4. If the rivet head does not come loose of its own accord, insert a drift punch into the hole and twist slightly to either side until the head comes off.
5. Drive the remaining rivet shank out with a drift punch slightly smaller than the shank diameter.

On thin metal or unsupported structures, support the sheet with a bucking bar while driving out the shank. If the shank is unusually tight after the rivet head is removed, drill the rivet about 2/3 through the thickness of the material and then drive the rest of it out with a drift punch. (*Figure 8-30*)

Rivet Removal

Remove rivets by drilling off the head and punching out the shank as illustrated.

1. File a flat area on the manufactured head of non-flush rivets.
2. Place a block of wood or a bucking bar under both flush and nonflush rivets when center punching the manufactured head.
3. Use a drill that is $\frac{1}{32}$ (0.0312) inch smaller than the rivet shank to drill through the head of the rivet. Ensure the drilling operation does not damage the skin or cut the sides of the rivet hole.
4. Insert a drift punch into the hole drilled in the rivet and tilt the punch to break off the rivet head.
5. Using a drift punch and hammer, drive out the rivet shank. Support the opposite side of the structure to prevent structural damage.

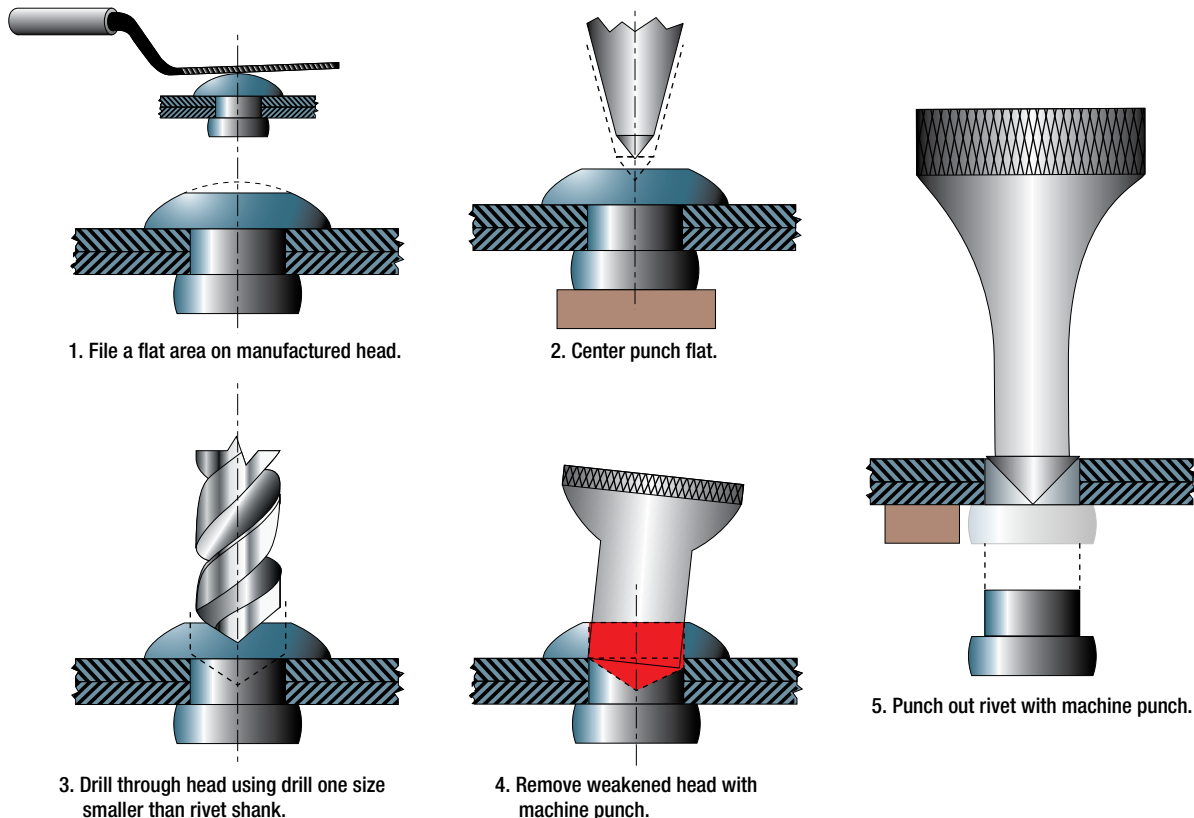


Figure 8-30. Rivet removal.

The procedure for the removal of countersunk rivets is the same as described above except no filing is necessary. Be careful to avoid elongation of the dimpled or the countersunk holes. The rivet head should be drilled to approximately one half the thickness of the top sheet.

To remove a countersunk or flush head rivet, you must:

1. Select a drill about 0.08 mm smaller than the rivet shank diameter.
2. Drill into the exact center of the rivet head to the approximate depth of the head.
3. Remove the head by breaking it off. Use a punch as a lever.
4. Punch out the shank. Use a suitable backup, preferably wood (or equivalent), or a dedicated backup block. If the shank does not come out easily, use a small drill and drill through the shank. Be careful not to elongate the hole.

REPLACING RIVETS

Replace rivets with those of the same size and strength whenever possible. If the rivet hole becomes enlarged, deformed, or otherwise damaged, drill or ream the hole for the next larger size rivet. Do not replace a rivet with a type having lower strength properties, unless the lower strength is adequately compensated by an increase in size or a greater number of rivets.

NACA METHOD OF DOUBLE FLUSH RIVETING

A rivet installation technique known as the National Advisory Committee for Aeronautics (NACA) method has primary applications in fuel tank areas.

To make a NACA rivet installation, the shank is upset into a 82° countersink. In driving, the gun may be used on either the head or shank side. The upsetting is started with light blows, then the force increased and the gun or bar moved on the shank end so as to form a head inside the countersink well. If desired, the upset head may be shaved flush after driving. The optimal strength is achieved by cutting the countersink well to the dimensions given. Material thickness minimums must be carefully adhered to. (*Figure 8-31*)

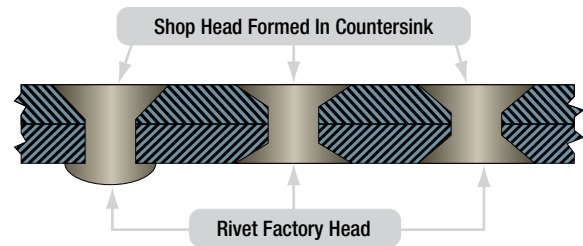


Figure 8-31. NACA riveting method.